



**Lesya Ukrainka Volyn National University**

**III International Scientific Conference**

**CURRENT PROBLEMS OF CHEMISTRY,  
MATERIALS SCIENCE  
AND ECOLOGY**

**Proceedings**

**2023**

**June 1-3,  
Lutsk, Ukraine**

УДК 54+66+574+615 (08)

A 43

*Рекомендовано до друку рішенням Вченої ради Волинського національного університету імені Лесі Українки (протокол № 7 від 25 травня 2023 року).*

Proceedings of III International Scientific Conference "Current problems of chemistry, materials science and ecology" are represented. These results were reported on the conference.

Edition of materials are made from author texts and prepared to printing the Program Committee and Editorial Board of conference.

Editorial Board: O.Yurchenko, Z.Kormosh, L. Gulay.

**Актуальні проблеми хімії, матеріалознавства та екології:**  
A 43 матеріали III Міжнародної наукової конференції (Луцьк, 1-3 червня 2023 року). – Луцьк: видавництво «Терен», 2023. – 186 с.

ISBN 978-617-8235-54-3

Збірник містить тези доповідей III Міжнародної наукової конференції, у яких викладені результати наукових досліджень у галузях хімії, хімічної технології, матеріалознавства, екологічної безпеки і охорони навколишнього середовища, технології хімічної освіти, фармації.

Редакційна колегія: Юрченко О.М., Кормош Ж.О., Гулай Л.Д.

**УДК 54+66+574+615 (08)**

ISBN 978-617-8235-54-3

©Волинський національний  
університет імені Лесі Українки,  
2023

## HIGH-Q CERAMICS WITH A NEAR-ZERO TEMPERATURE COEFFICIENT AT MICROWAVE FREQUENCIES

*Plutenko T.*<sup>1</sup>, *Fedorchuk O.*<sup>1</sup>, *Torchyniuk P.*<sup>1</sup>, *V'yunov O.*<sup>1</sup>, *Belous A.*<sup>1</sup>

<sup>1</sup>V.I. Vernadsky Institute of General and Inorganic Chemistry, Kyiv, Ukraine

[taplutenko@gmail.com](mailto:taplutenko@gmail.com)

With the rise of the 5G era, there is growing interest in microwave dielectric ceramics. These ceramics serve not only as insulating substrates in microwave circuits but also as essential materials for various microwave communication technologies such as dielectric resonators, filters, oscillators, phase shifters, and capacitors. Consequently, microwave components play a crucial role in the miniaturization, integration, and cost reduction of modern communication devices. For 5G technology, dielectric materials exhibiting high dielectric constant, high  $Q_f$  value, near-zero temperature coefficient of resonance frequency, and low sintering temperature are highly desirable.

Materials based on calcium titanate exhibit a high  $Q$ -factor ( $Q_f = 10700$  GHz) and possess a positive temperature coefficient of the resonant frequency. Conversely, ceramics composed of  $\text{Ln}(\text{Mg}_{0.5}\text{Ti}_{0.5})\text{O}_3$  with a perovskite structure have a  $Q_f$  value ranging around 40,000 and display a significantly negative  $\tau_f$  value (approximately  $-70 \times 10^{-6}/^\circ\text{C}$ ). By combining calcium titanate materials with  $\text{Ln}(\text{Mg}_{0.5}\text{Ti}_{0.5})\text{O}_3$  ceramics, it becomes feasible to create microwave dielectric ceramics with moderate values of  $\epsilon$ , high  $Q_f$ , and  $\tau_f$  values approaching zero. So far, there is limited existing literature data on the production of ceramics through the amalgamation of materials possessing positive and negative  $\tau_f$ . This study employed high-temperature sintering to fabricate  $(\text{Ca}_{2/3x}\text{La}_{1/3x}\text{Nd}_y)(\text{Mg}_{0.5y}\text{Ti}_{0.5y+x})\text{O}_3$  ceramics and conducted a comprehensive examination of the impact of the sintering process and component ratios on their microstructure and microwave dielectric properties.

The  $(\text{Ca}_{2/3x}\text{La}_{1/3x}\text{Nd}_y)(\text{Mg}_{0.5y}\text{Ti}_{0.5y+x})\text{O}_3$  ceramics were synthesized using the solid-state reaction method. The raw materials, including high-purity  $\text{CaCO}_3$ ,  $\text{La}_2\text{O}_3$ ,  $\text{Nd}_2\text{O}_3$ ,  $\text{MgO}$ , and  $\text{TiO}_2$  powders, were mixed using a ball mill for 8 hours. The mixture was then dried for 24 hours, ground, sieved, and subjected to individual calcination processes (at  $1200^\circ\text{C}$  for 3 hours). Subsequently, the calcined powders were mixed using a ball mill for 8 hours, dried for 24 hours, and sieved. A polyvinyl alcohol solution (PVA) was added as a binder, and the mixed powders were pressed into cylindrical specimens with a diameter of 10 mm and a thickness of 4 mm. These specimens were then sintered in air ( $1600^\circ\text{C}$ , 30 minutes). The samples were crushed, ground, and subjected to phase analysis using X-ray diffraction (XRD). The microstructures of the samples were observed using a scanning electron microscope (SEM). To measure the dielectric properties, polished cylindrical specimens of ceramics were placed in a metal cavity of a vector network analyzer. The dielectric constant ( $\epsilon$ ), quality factor ( $Q$ ), and temperature coefficient of resonant frequency ( $\tau_f$ ) were measured at  $25^\circ\text{C}$ .

The density initially increased with increasing sintering temperature but started to decrease after reaching a certain point, indicating the occurrence of oversintering. The data clearly show that  $\rho$  increases with increasing  $x$ , reaching a maximum value of 5.4. This can be attributed to the higher density of  $\text{Ln}(\text{Mg}_{0.5}\text{Ti}_{0.5})\text{O}_3$  ceramic compared to  $\text{CaTiO}_3$ -based

ceramic. The diffraction peaks show significant overlap, indicating the presence of a perovskite structure without any secondary phase (Fig.1).

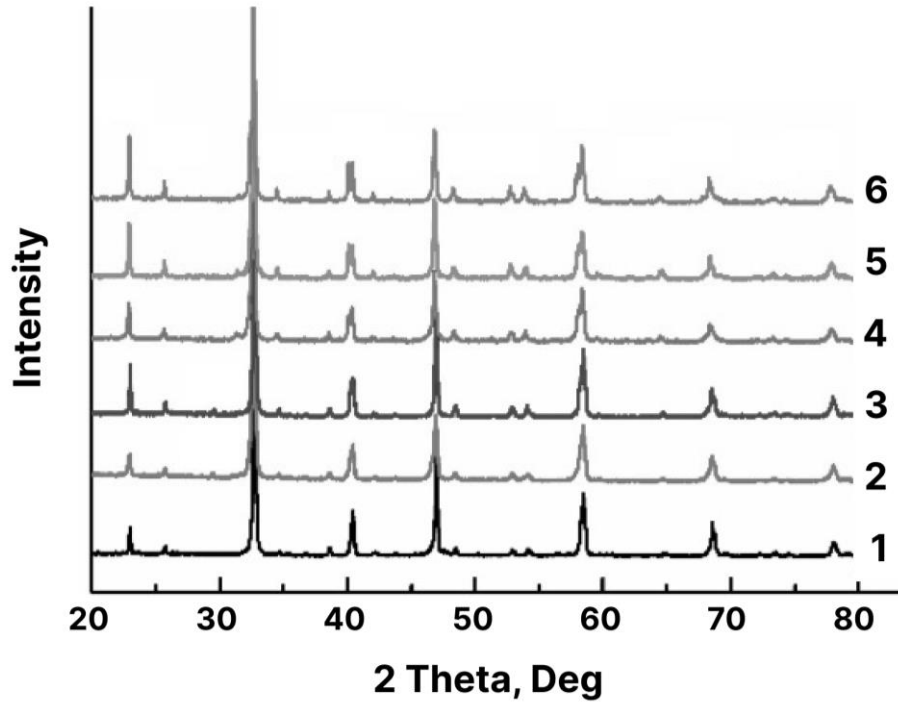


Fig. 1. XRD spectra for  $(Ca_{2/3x}La_{1/3x}Nd_y)(Mg_{0.5y}Ti_{0.5y+x})O_3$  where  $x=0.3$  (1), 0.35 (2), 0.4 (3), 0.45 (4), 0.5 (5), 0.55 (6).

However, superlattice diffraction peaks are observed at  $x = 0.40$ . Main diffraction peaks of  $(Ca_{2/3x}La_{1/3x}Nd_y)(Mg_{0.5y}Ti_{0.5y+x})O_3$  ceramics shift towards lower angles as  $x$  increases. This shift suggests an increase in the lattice constant of the perovskite structure. The lattice constant and unit cell volume gradually increase with increasing  $x$ , consistent with the XRD analysis. This trend is influenced by two factors: the decreasing vacancy concentration in the A-site and the increasing  $Mg^{2+}$  content ( $r(Mg^{2+}) > r(Ti^{4+})$ ) in the B-site.

For  $x \leq 0.5$ , the grain size ranges from 20 to 40  $\mu m$  and shows relatively uniform distribution with minimal changes as the  $x$  content increases. As  $x$  increases,  $\epsilon$  gradually decreases from 50 to 35 due to the lower dielectric constant of  $Ln(Mg_{0.5}Ti_{0.5})O_3$  compared to  $CaTiO_3$ . The  $Q_f$  initially increases from 14000 GHz ( $x = 0.30$ ) to 16000 GHz ( $x = 0.6$ ). The results indicate that  $\tau\epsilon$  is primarily influenced by the tilt of the  $BO_6$  octahedron. Increasing tilt of the  $BO_6$  octahedron leads to a positive change in  $\tau\epsilon$ . The tilt degree of the  $BO_6$  octahedron can be described by the tolerance factor: a greater difference between the  $t$  value and 1 indicates a higher tilt degree. There is a regular pattern between  $\tau\epsilon$  and  $t$ : when  $t < 0.965$ , a decrease in  $t$  leads to a positive change in  $\tau\epsilon$ . In the case of  $(Ca_{0.61x}La_{0.26x}Nd_y)(Mg_{0.5y}Ti_{0.5y+x})O_3$  ceramics, a decrease in the  $t$  value results in an increased tilt degree of the  $BO_6$  octahedron. Consequently,  $\tau\epsilon$  increases, and  $\tau f$  decreases in the negative direction.

**Acknowledgment:** This work was supported in part by the NATO Science for Peace and Security Programme within the framework of the "3D Metamaterials for Energy Harvesting and Electromagnetic Sensing" project (ID SPS G6002).

Наукове видання

**CURRENT PROBLEMS OF CHEMISTRY,  
MATERIALS SCIENCE AND ECOLOGY**

**Proceedings III International Scientific Conference**

Укладач: Юрченко О.М.

Друкується в авторській редакції

Підписано до друку 06.06.2023 р. Формат 60x84 1/16.

Ум. друк. арк. 11,62. Замовлення № 78. Тираж 100.

Папір офсетний. Гарнітура Times. Друк офсетний.

Видавництво Терен. 43025, м. Луцьк, вул. Гаврилюка, 14.

Тел.: 050-2956548, 096-5880970, [teren.lutsk@gmail.com](mailto:teren.lutsk@gmail.com)

Свідоцтво Державного комітету телебачення і радіомовлення України  
ДК №1508 від 26.09.2003 р.

Віддруковано з готових діапозитивів на ПП Іванюка В. П.

43021, м. Луцьк, вул. Винниченка, 65.

Свідоцтво Держкомінформу України ВЛн № 31 від 04.02.2004 р.